


# Wood Identification for Hardwood and Softwood Species Native to Tennessee

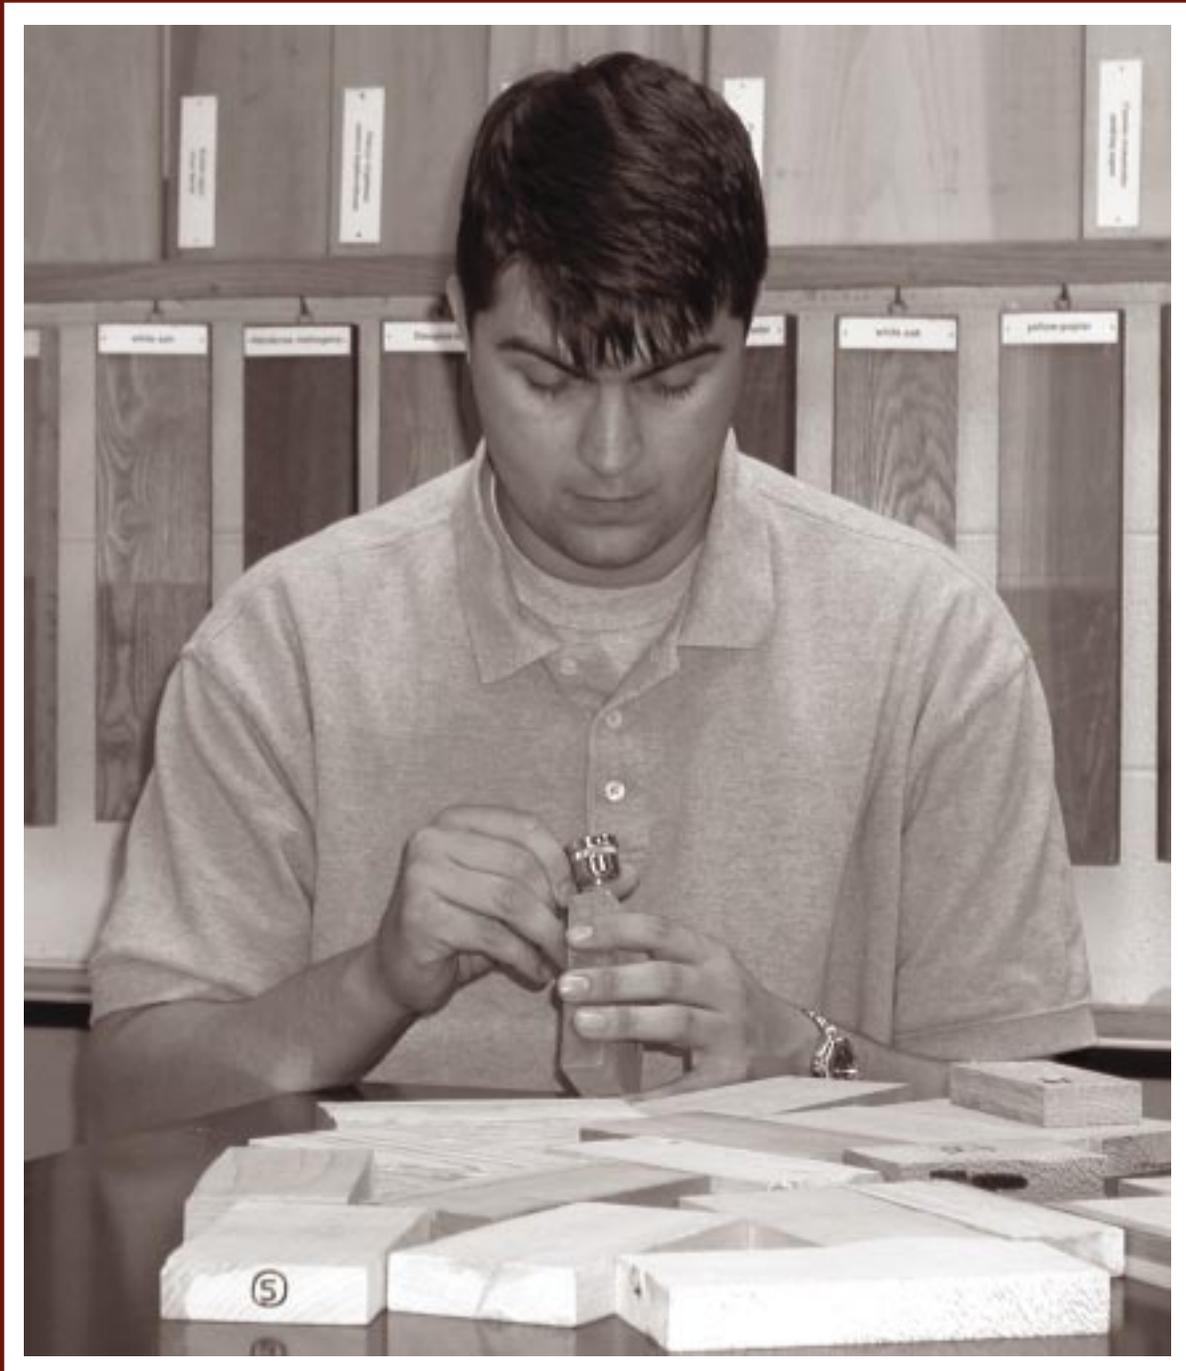

# Contents

**Introduction 3**

**Wood Surfaces 3**

**Macro Cross-section Characteristics 4**

**Preparing the Wood Surface 4**

**Separating Hardwoods from Softwoods 4**

**Hardwoods 6**

Growth Ring Pore Arrangement 6

Vessel (Pore) Arrangement 6

Wood Rays 7

Tyloses 7

Parenchyma 7

Color, Odor and Density 8

**Softwoods 8**

Resin Canals 8

Growth Rings: Earlywood and Latewood 8

Color, Odor and Density 9

**Summary 9**

**Other Publications Related to Wood Identification 10**

**Wood ID: Species Characteristics 11**

Ring-Porous Hardwoods 11

Semi-Ring-Porous Hardwoods 12

Diffuse-Porous Hardwoods 12

**Softwood Identification 12**

**Softwood Key 14**

**Hardwood Key 15**

# Wood Identification for Hardwood and Softwood Species Native to Tennessee

*Brian Bond, Assistant Professor, and Peter Hamner, Research Associate  
Department of Forestry, Wildlife and Fisheries  
The University of Tennessee*

## Introduction

This publication provides information on how to identify wood of several species common to Tennessee by using a hand-magnifying lens. Included in this publication are a wood identification key for some common Tennessee species, a list of key specie characteristics and a list of companies that sell wood identification sample sets.

Tennessee has a rich variety of tree species, and the wood produced from each of these has unique structure, physical and mechanical properties. The differences in wood structure and properties allow for the manufacture of wood-based products with many different appearances and uses. Since wood is a popular and useful material, it is important that enthusiasts and professionals be able to distinguish the wood of one species from another. For example, how would a barrel manufacturer tell the difference between red oak, which doesn't hold liquids, and white oak, which does?

Wood of a particular species can be identified by its unique features. These features include strength, density, hardness, odor, texture and color. Reliable wood identification usually requires the ability to recognize basic differences in cellular structure and wood anatomy. Each species has unique cellular structure that creates differences in wood properties and ultimately determines the suitability for a particular use. Cellular characteristics provide a blueprint for accurate wood identification.


Wood is composed of many small cells and its structure is determined by the type, size, shape and arrangement of these cells. The structure and characteristics of wood can vary between species and within the same species. With practice, a small

hand lens (10x) can be used to distinguish the different cell types and their arrangements. By using the proper techniques, you can become efficient and accurate at wood identification.

## Wood Surfaces

Most of the wood cell structure characteristics discussed in this publication are best viewed from the **cross-section** surface of the wood. Wood surfaces are classified into three categories, or geometric planes of reference, that indicate the type of surface uncovered after a cut has been made. The three reference planes are the cross section, radial section and tangential section.

**Figure 1** depicts the three reference planes of wood. The cross section is produced by cutting the cells perpendicular to the direction of growth in the tree. The cross section is the same surface seen on

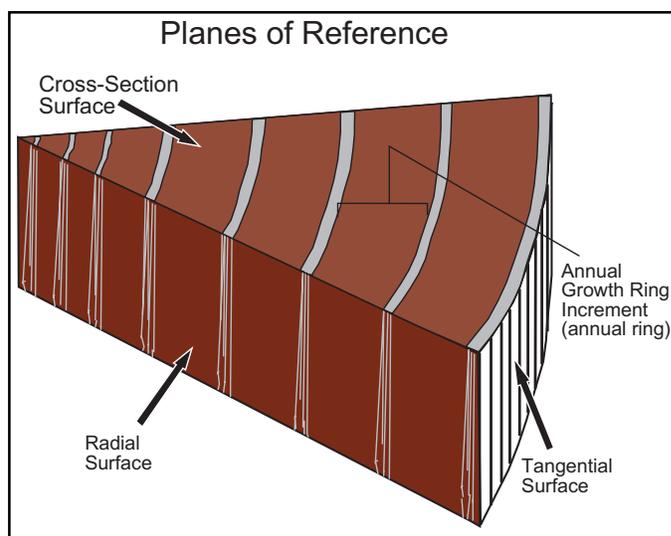

**Figure 1.** Three-dimensional orientation of wood material.

a stump after felling a tree. It is important to determine which reference plane you are viewing when identifying wood, because cell structure is three-dimensional and varies based on orientation.

## Macro Cross-section Characteristics

By cutting a tree and exposing the cross section, you can observe the bark, phloem (bark-producing layer), cambium (a thin layer inside the bark where cell division takes place) and xylem (sapwood and heartwood) (**Figure 2**). The heartwood is the darker-colored material that is formed in the center of the tree. Although heartwood is formed in the tree center, it may not occur uniformly across the surface of the section. The heartwood contains extractives, which are the chemical components that give cedar its pleasant aroma, redwood its decay resistance and walnut its dark color. The sapwood surrounds the heartwood and is lighter-colored. The size and width of the sapwood will vary greatly between species. For example, the sapwood of locust is a very narrow outer band and the sapwood of black cherry is very wide. The color and odor of heartwood can also be useful in identifying certain species like redcedar, sassafras and black walnut.

Another feature that can be observed when viewing the cross section is the growth rings. A growth ring represents one year of wood forma-

tion. The development of the wood material inside a growth ring is caused by the changes that occur during the growing season. Earlywood, or springwood, is formed in the spring and early summer at the beginning of the growing season when warm and wet conditions promote rapid growth. Earlywood cells have large diameters and thin cell walls. Latewood, or summerwood, is formed in late summer and fall toward the end of the growing season when dryer conditions slow the development of new wood growth. Latewood occurs at the outer region of a growth ring, and is characterized by cells with greatly thickened cell walls and narrow diameters.


## Preparing the Wood Surface

To view the cellular characteristics of wood, it is very useful to have a 10-power (10x) hand lens to magnify the section you are looking at. Preparation of the wood surface is important and can affect your ability to locate and identify specific cell types. The cross section is the best section to begin your observation of the cell structure in wood. To prepare a cross section for viewing, make a thin, clean cut with a razor blade or sharp knife. Make the cut across the surface at a slight angle. It is important not to take off too much material or to cut too deeply. You are better to make several thin slicing cuts to enlarge the viewing area rather than trying to make one large cut. Using a dull blade or cutting too deeply will create a poor surface and mask otherwise useful identifying features. Only a small area with a few growth rings is needed for adequate observation and identification.

Identifying wood is a process of elimination. The best strategy is to search for particular features that will help you to categorize the species or group of species with those features, and thus eliminate others that do not. The use of an identification key can be helpful for this separation. A wood identification key is provided for the species discussed in this publication.

## Separating Hardwoods from Softwoods

After preparing a surface to view, the first step is to determine whether a specimen is softwood or a hardwood. The terms softwood and

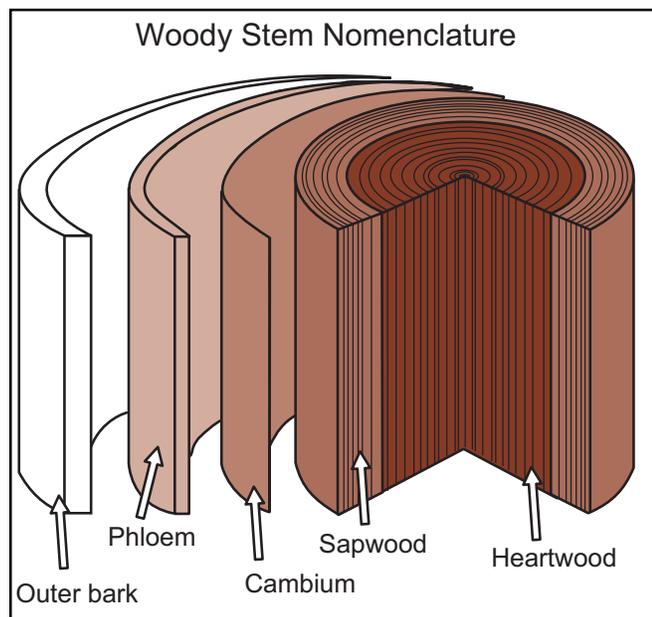

**Figure 2.** Primary layers of wood tissue through the diameter of a tree.

hardwood are used to reference the taxonomical division that separates a species and have little to do with the actual hardness of the wood. Hardwood trees have broad leaves and are deciduous – they lose their leaves at the end of the growing season. Hardwoods are angiosperms – using flowers to pollinate for seed reproduction. Oaks, maples, birches and fruit trees are examples of hardwood trees. Softwood trees are conifers (evergreens), have needles or scale-like foliage and are not deciduous. Softwoods are gymnosperms, meaning they do not have flowers and use cones for seed reproduction. Examples of softwoods include pines, spruces, firs and hemlocks.

Softwood cellular structure is simple and 90-95 percent of the cells are **longitudinal tracheids**. Longitudinal tracheids function in water conduction and support. The limited number of cell types makes softwoods more difficult to differentiate from one another.


Hardwood structure is more complex than softwood structure, and varies considerably between species. The majority of hardwood volume is composed of fiber cells that offer structural support to the stem. The major difference between hardwoods and softwoods is the presence of **vessel elements**, or **pores**, that exist in hardwoods only. The main function of vessel elements is water conduction. Vessel elements can vary greatly in size, number and spacing from one species to another, and from earlywood to latewood. Some species, like oak, have vessel elements that are

### How to prepare a good surface for viewing wood structure with a hand lens

- A sharp blade is required for good surface preparation. A razor blade is best.
- A good clean surface is one where cells have been cleanly cut rather than torn.
- Do not cut too deep. Deep cuts will result in torn fibers in the wood section and possible injury to your hands and fingers!
- Only a few growth rings on the cross section are needed.
- Wetting the surface with water can be helpful in getting a good, clean section.

extremely large and numerous. Other species, such as yellow-poplar, gum and birch, have vessel elements that are uniform in size and number, and are evenly spaced throughout the growth ring. By using a hand lens, you can determine if vessel elements are present or not, thus separating hardwoods from softwoods. **Figure 3** illustrates the three dimensional differences between hardwood and softwood cell structure.

After determining whether a wood sample is a hardwood or softwood – based on the presence or absence of vessel elements – we can begin to look more closely at other cell types for further assistance with identification.

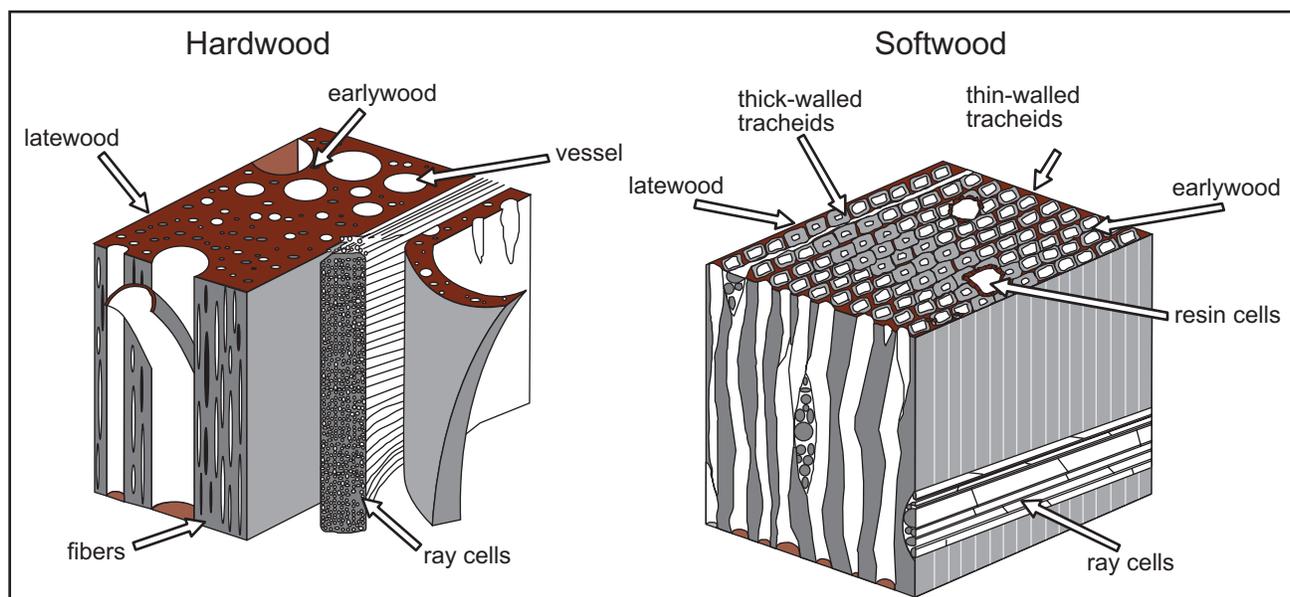

**Figure 3.** Three-dimensional cell level comparison between hardwood and softwoods.

# Hardwoods

## Growth Ring Pore Arrangement

The next major step in identifying hardwoods is to observe and categorize how the change, or transition, in pore size occurs from earlywood to latewood within a growth ring. There are three general classifications for this earlywood/latewood transition, as depicted in **Figure 4**.

- (1) **Ring-porous hardwoods (Figure 4a)**. For some groups of species (oaks and elms) the earlywood/latewood transition occurs abruptly and is very distinct. Within each growth ring, a band of large earlywood vessels (pores) is clearly visible to the naked eye, after which a band of latewood vessels appears much smaller and requires the use of a hand lens to see.
- (2) **Semi-ring-porous hardwoods (Figure 4b)**. For another group of species (black walnut, butternut and hickory) the pore transition from large to small diameter within a growth ring is gradual. The pores in the earlywood zone have a large

diameter that gradually decreases in size as pores enter the latewood zone.


- (3) **Diffuse-porous hardwoods (Figure 4c)**. The last group of species has vessels (pores) that are uniform in size across the entire growth ring (yellow poplar, gum and maple). These vessels are usually small, uniform in size and are very difficult to see with the naked eye (a hand lens is needed).

## Vessel (Pore) Arrangement


Vessel elements (pores) can be described by their position relative to each other in a cross section. Different species have unique vessel arrangements. **Figure 5** shows some of the more common vessel arrangements.

**Solitary pores (Figure 5a)**: single pores that do not touch any other pores – evenly spaced across cross section (maples).

**Pore multiples (Figure 5b)**: arrangement where two to five pores appear grouped together.

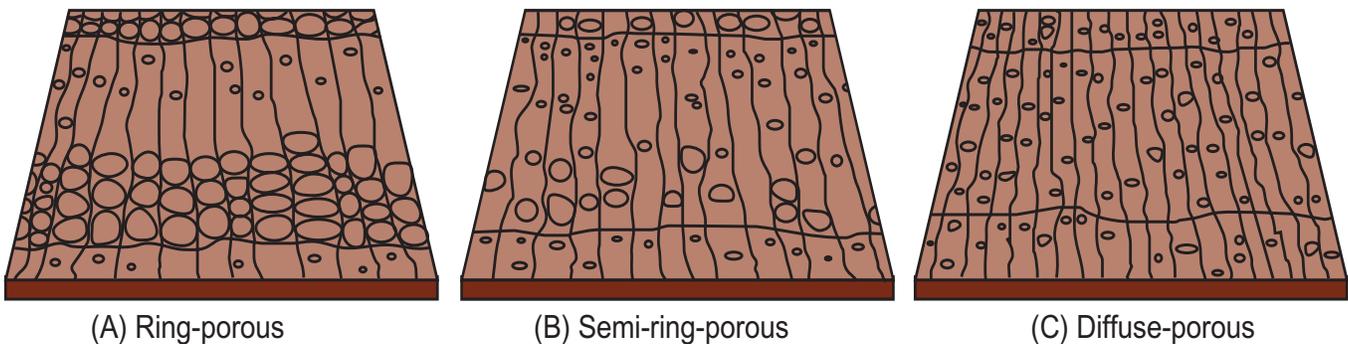

**Figure 4.** Classification of pore transition from earlywood to latewood.

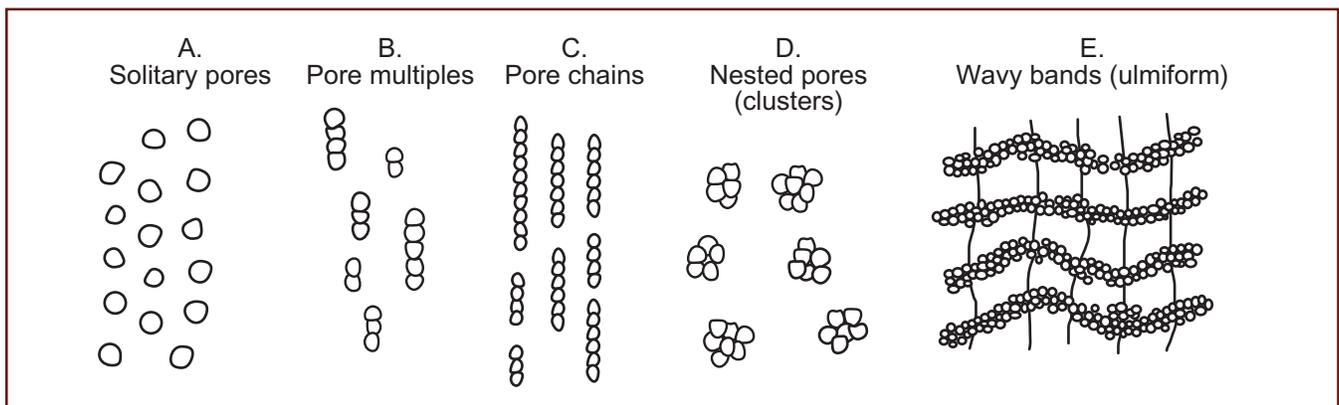

**Figure 5.** Vessel (pore) arrangement.

Pore multiples usually occur in radial rows (cottonwood), but can occur in both radial and tangential directions (Kentucky coffeetree).

**Pore chains (Figure 5b):** arrangement where pore multiples appear in radial direction only.

**Nested pores (Figure 5c):** when larger numbers of pores contact each other both radially and tangentially (cluster).

**Wavy bands (Figure 5d):** Pores are arranged in irregular concentric bands. Also called *ulmiform* because this characteristic is distinctive of all elms (also hackberry).

## Wood Rays

Once the pore distribution and arrangement have been identified, it is important to look at the size and arrangement of **wood rays**. Wood rays are seen as narrow stripes or lines that extend across the growth rings in the radial direction – from the bark to the center of the tree. Wood rays function to transport food and water horizontally across the diameter of a tree.

The size and distribution of rays on the cross section are quite unique for many species and groups of species. Species such as red and white oak have very wide rays (many cells wide) that are easily seen without a hand lens. Species such as yellow-poplar, ash and maple have numerous and extremely narrow rays (just 1-2 cells wide). The distribution of rays can also be used to separate some species. For example, beech and sycamore both have large, conspicuous rays with fine, narrow rays running between them. Another useful characteristic of rays that can be observed on the cross section of some species is the presence of *nodes*, or a swelling of the ray, at the intersection of a new growth ring – where the earlywood zone begins. Ray nodes are seen in yellow-poplar, beech and sycamore.

When viewing a piece of wood from either the radial or tangential surface, wood rays can be a key characteristic to help identify the species. Rays vary not only in width, but also in height. The height of a ray is best observed from the tangential surface. Ray height varies between species from imperceptibly small to several inches high. For example, in red oak, ray height never exceeds 1 inch, while in white oak, the height of the rays are consistently greater than 1¼ inch.

When wood is cut radially, across the plane where rays extend through the diameter of the cross section surface, many rays are split and exposed in patches on the radial surface. In many species – maple, sycamore and beech especially – these patches of split rays contrast in color from the longitudinal tissue around them and form a freckled pattern on the radial surface called *ray fleck*.

## Tyloses


Tyloses are inclusions that form inside the vessels of some hardwoods. Because tyloses are unique to certain hardwood species, they are useful for wood identification. Tyloses are outgrowths of parenchyma cells into the hollow lumens of vessels and they look like bubbles or cellophane-like structures clogging the openings of the vessel elements. Tyloses may be absent or sparse, as in red oak; variable, in the case of chestnut and ash; or densely packed and abundant, as they appear in white oak and locust. Tyloses effectively clog the vessels and subsequently restrict moisture movement. The presence of tyloses is the reason white oak is used for making whisky barrels.

## Parenchyma

Parenchyma are small, thin-walled, longitudinal cells that provide food storage. These cells are sparse in softwoods but are often quite significant in hardwoods. Parenchyma are often very small and difficult to see. However, there are many species with visible and unique arrangements of parenchyma cells that offer a clear structural feature for decisive identification.

There are two basic types of parenchyma: *paratracheal* and *apotracheal*. The major difference between them is that paratracheal parenchyma make contact with the pores or vessel elements, while apotracheal parenchyma are separated from pores by fibers or rays. **Figure 6** shows the various types of paratracheal and apotracheal parenchyma.

In most species, apotracheal parenchyma are not be useful in identifying wood with just a hand lens. One exception is yellow-poplar, which has a fine, clear, bright line of marginal apotracheal parenchyma at the edge of every growth ring. Since yellow poplar is a diffuse porous species, the presence of marginal parenchyma aids tremendously in its identification. Paratracheal parenchyma appears in many forms, and is often more

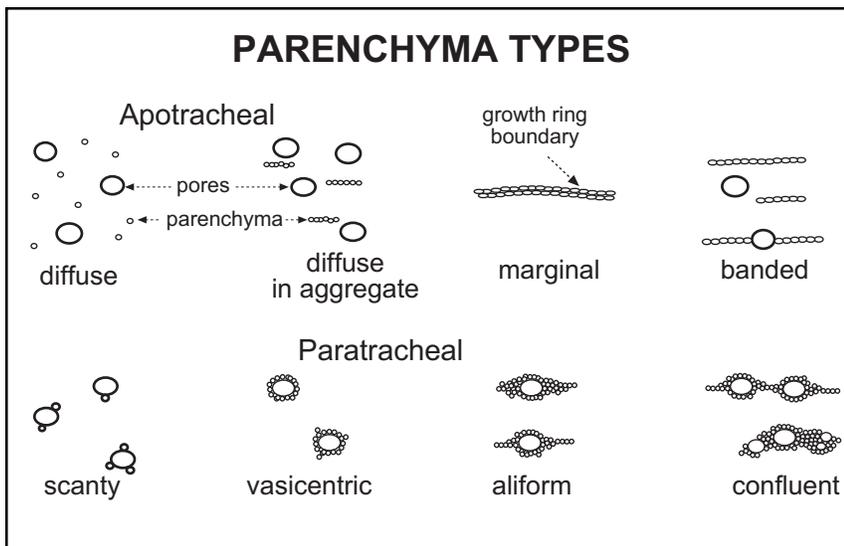

**Figure 6.** Classification of parenchyma arrangements around hardwood pores. (cross-section view)

useful for identification. For example, in hickory the banded parenchyma looks like a reticulate, “web-like” formation as it connects between the rays and pores. This “web-like” appearance is unique to hickory.

### Color, Odor and Density

Other characteristics of wood species that are fundamental to wood identification include: color, odor and density. These characteristics are remarkably variable in hardwoods and often provide the first clue to identify a particular wood species. Hardwoods come in a variety of colors and shades that often allow immediate and unmistakable recognition. Consider the lush reddish brown of black cherry, the deep chocolate brown of black walnut or the creamy white of hard maple.

Less obvious, but certainly helpful to wood identification are odor characteristics. Many hardwoods have distinctive natural odors. Black cherry, for example, has an unmistakably fragrant aroma, while red oak is more bitter and acidic smelling.

Hardwoods also vary significantly with respect to density. The density of wood is related to its hardness, strength and weight. Typically, a dense species of wood is heavier, harder and stronger than other, less dense species. Hardness is particularly useful when distinguishing between hard and soft maple. Soft maple can be easily dented with your fingernail or sliced with a razor blade, while hard maple is significantly more difficult to make an impression. Hickory, black

locust and osage-orange are quite heavy compared to most other species. It is often helpful to keep in mind how difficult or easy it is to make a cut on the cross section of a piece of wood when preparing the surface for examination.

## Softwoods

### Resin Canals

The first step after making the determination that a wood specimen is softwood – due to the absence of pores – is to inspect the cross-section surface for the presence of resin canals. **Resin canals** are tubular passages in wood that exude pitch, or resin, to seal off wounds that occur due to

insect or mechanical damage. Resin canals most often occur in or near the latewood zone of the growth rings. Softwoods can be separated into two classifications based on the presence or absence of resin canals. Species that have resin canals include pines, spruces, larches and Douglas-fir. The species that do not have resin canals include firs, hemlocks, cedars, redwood, baldcypress and yew.

Woods with resin canals are further separated into two groups: (1) those with large resin canals – pines, and (2) those with small resin canals – Douglas fir, spruce and larch. Using a sample wood identification set to compare the size and number of resin canals of different species is useful in determining how much they can differ between species. For example, most pines have quite large and numerous resin canals that can be seen without the aid of a hand lens. Spruce and larch, on the other hand, have much smaller resin canals that occur less frequently. Douglas fir has many small resin canals. Because the presence of resin canals is quite variable, it may be necessary to make several cuts on the cross section of a specimen to uncover enough surface area to make a good determination.

### Growth Rings: Earlywood and Latewood

In softwoods, earlywood/latewood characteristics can provide useful information for identification. The features to compare are: (1) the nature of the earlywood/latewood transition – abrupt or

gradual, and (2) the percentage of latewood occupying the growth ring.

When identifying hardwoods, the size and distribution of pores between earlywood and latewood are discriminating factors. Since softwoods have no pores, the difference between the earlywood and latewood zones in the growth ring occurs due to effects that the growing season has on the longitudinal tracheids (the dominant cell type in softwoods). The earlywood zone of a growth ring typically consists of thin-walled, larger-diameter cells, while the latewood zone features thick-walled, smaller-diameter cells. Thus, for many species, the earlywood zone appears lighter, contrasting with the latewood zone, which is often a darker or browner shade.

For some species the transition from the lighter-colored earlywood to the darker-colored latewood is distinct and abrupt (southern yellow pine, Douglas fir, redwood). For other woods, this transition is extremely gradual and even imperceptible (white pine, cedars). Some species have an earlywood and latewood transition that falls between gradual to abrupt (spruce, fir, hemlock).

### **Color, Odor and Density**

As with the hardwoods, color, odor and density are useful characteristics in identifying softwoods. Some species have distinct color differences, while others do not. Eastern white pine is consistently yellowish white, darkening to light brown with age. Eastern redcedar has a distinctive deep purplish-red color, and redwood a deep reddish-brown. Examples of odors include the “piney” fragrance of pines, the “cedar chest” scent of eastern redcedar and the relative absence of smell in spruce, firs and hemlocks.

Softwoods also vary substantially in density. Because many species are quite dense and strong, softwood lumber is typically used for structural or construction purposes. Southern yellow pine, spruce, hemlock, fir and Douglas fir are all commonly used in the construction industry. White pine and cedars, on the other hand, are considerably less dense and lighter in weight than the other species, while white pine and cedars are easier to slice with a razor blade when preparing a surface for identification.

## **Summary**

Becoming familiar with wood characteristics and structure, as well as the techniques used to identify them, requires practice and dedication. If you know what to look for and where to look, your eye can be trained to pick up unique wood characteristics, enabling accurate and efficient wood identification. While this publication outlines the general principles of wood identification using a hand lens, anyone seeking more in-depth and complete methods should refer to one of the publications listed below.

## **Other Publications Related to Wood Identification**

Panshin, A. J. and C. de Zeeuw. *Textbook of Wood Technology*. McGraw-Hill. 1980.

Hoadley, R. B. *Identifying Wood: Accurate Results with Simple Tools*. Taunton Press, Inc. Newton, CT. 1990.

*Woods of the World* CD-ROM. Tree Talk Inc. 1994. Burlington, VT.

Sources of Wood Samples for Identification  
Carolina Biological Supply Company  
2700 York Road  
Burlington, NC 27215  
919-584-0381

International Wood Collectors Society  
13249 Hwy. 84 N  
Cordova, IL 61242-9708  
309-523-2852

Wisconsin Crafts  
W6407 20<sup>th</sup> St.  
Necedah, WI 54646  
608-565-2101

Garret Wade Company  
161 Avenue of the Americas  
New York, NY 10013  
1-800-221-2912

Educational Lumber Co., Inc.  
Box 5373  
Asheville, NC 28803  
704-255-8765

# Wood ID: Species Characteristics

## Ring-porous hardwoods

### American Elm

*Ulmus Americana*

**Average specific gravity:** 0.50

**Heartwood color:** Light brown to brown or reddish brown

**Pore distribution:** Ring-porous

**Earlywood:** Pores large, in continuous row

**Latewood:** Pores in wavy bands

**Tyloses:** Present in earlywood, but usually sparse

**Rays:** Not distinct without lens; homogeneous 1-7 (mostly 4-6) seriate.

### Ash

*Fraxinus spp.*

**Average specific gravity:** 0.60

**Heartwood color:** Light brown or grayish brown.

**Sapwood color:** Creamy white (may be very wide)

**Pore distribution:** Ring-porous

**Earlywood:** 2-4 pores wide; pores moderately large, surrounded by lighter tissue

**Latewood:** Pores solitary and in radial multiples of 2-3, surrounded by vasicentric parenchyma or connected by confluent parenchyma in outer latewood. Thick-walled.

**Tyloses:** Fairly abundant (some vessels open)

**Rays:** Not distinct to eye, but clearly visible with lens; 1-3 seriate

### Black Locust

*Robinia pseudoacacia*

**Average specific gravity:** 0.69

**Heartwood color:** Olive or yellow-brown to dark yellow-brown; dark russet brown with exposure

**Fluorescence:** Bright yellow

**Sapwood:** Never more than 3 growth rings wide

**Pore distribution:** Ring-porous

**Earlywood:** 2-3 pores wide; pores large.

**Latewood:** Pores in nest-like groups, which merge into interrupted or somewhat continuous bands in outer latewood; latewood fiber mass appears dense and dark in contrast to yellowish; tyloses filled pores and rays.

**Tyloses:** Extremely abundant with yellowish cast and sparkle, solidly packing vessels and making adjacent pores indistinct.

**Rays:** 1-7 (mostly 3-5) seriate

### Hickory

*Carya spp.*

**Average specific gravity:** 0.72

**Heartwood color:** Light to medium brown or reddish brown

**Pore distribution:** Ring-porous

**Earlywood:** Mostly an intermittent single row or thick-walled pores with fiber mass where interrupted

**Latewood:** Pores not numerous, solitary and in radial multiples of 2-5. Thick-walled.

**Tyloses:** Moderately abundant

**Rays:** 1-4 seriate

**Parenchyma:** Banded parenchyma and rays form a reticulate pattern distinctly visible against the background fiber mass with a hand lens (but banded parenchyma absent from earlywood zone)

### Northern Red Oak

*Quercus rubra*

**Average specific gravity:** 0.63

**Heartwood Color:** Light brown, usually with flesh or pinkish-colored cast.

**Pore Distribution:** Ring-porous

**Earlywood:** Up to 4 or 5 rows or large solitary pores.

**Latewood:** Pores solitary in radial lines, few and distinct ("countable"), vessels thickwalled

**Tyloses:** Absent or sparse in earlywood

**Rays:** Largest rays conspicuous; tallest less than 1 in. (tangential surface). Narrow rays uniseriate (one cell wide) or in part bisariate

### White Oak

*Quercus alba*

**Average specific gravity:** 0.68

**Heartwood color:** Light to dark brown to grayish brown.

**Pore Distribution:** Ring-porous

**Earlywood:** Up to 4 rows of large pores

**Latewood:** Pores small, solitary or in multiples, in spreading radial arrangement, numerous and indistinct ("uncountable"), grading to invisibly small with lens. Vessels thin-walled.

**Tyloses:** Abundant

**Rays:** Largest rays conspicuous; tallest greater than 1<sup>1</sup>/<sub>4</sub> in. Narrow rays uniseriate or in part bisariate.

## Semi-Ring-Porous Hardwoods

### Black Walnut

*Juglans nigra*

**Average specific gravity:** 0.55

**Heartwood color:** medium brown to deep chocolate brown

**Pore distribution:** semi-ring-porous

**Pores:** earlywood pores fairly large, decreasing gradually to quite small in outer latewood; pores solitary or in radial multiples of 2 to several

**Tyloses:** Moderately abundant

**Rays:** fine, visible but not conspicuous with hand lens, 1-5 seriate, cells appear round in tangential view

**Crystals:** Occur sporadically in longitudinal parenchyma cells

## Diffuse-Porous Hardwoods

### American Basswood

*Tilia americana*

**Average specific gravity:** 0.37

**Heartwood color:** Creamy white to pale brown

**Odor:** Faint but characteristic musty odor

**Pore distribution:** Diffuse-porous; growth rings indistinct or faintly delineated by marginal parenchyma, sometimes with blurry whitish spots along the growth ring boundary

**Pores:** Small, mostly in irregular multiples and clusters

**Rays:** Distinct but not conspicuous on transverse surface with lens. 1-6 seriate; ray cells appear laterally compressed in tangential view; rays have bright yellow cast

### American Beech

*Fagus grandifolia*

**Average specific gravity:** 0.64

**Heartwood color:** Creamy white with reddish tinge to medium reddish-brown

**Pore distribution:** Diffuse porous; growth rings distinct.

**Pores:** Small, solitary and in irregular multiples and clusters, numerous and evenly distributed throughout most of the ring; narrow but distinct latewood in each ring due to fewer, smaller pores

**Rays:** Largest rays conspicuous on all surfaces; darker ray fleck against lighter background on radial surfaces. Largest rays 15-25 seriate; uniseriate rays common

### Black Cherry

*Prunus serotina*

**Average specific gravity:** 0.50

**Heartwood color:** Light to dark cinnamon or reddish-brown

**Pore distribution:** Diffuse-porous; growth rings sometimes distinct because of narrow zone or row of numerous slightly larger pores along initial earlywood.

**Pores:** Pores through growth ring solitary and in radial or irregular multiples and small clusters

**Gum Defects:** Common

**Rays:** Not visible on tangential surface; conspicuous light ray fleck on radial surfaces; distinct bright lines across transverse surface, conspicuous with lens. 1-6 (mostly 3-4) seriate.

### Black Gum

*Nyssa sylvatica*

**Average Specific Gravity:** 0.50

**Heartwood Color:** Medium grey or grey with green or brown cast (wood usually has interlocked grain)

**Pore Distribution:** Diffuse-porous

**Pores:** Very small, numerous, solitary and in multiples and small clusters

**Rays:** Barely visible even with hand lens; 1-4 seriate

### Eastern Cottonwood

*Populus deltoides*

**Average specific gravity:** 0.40

**Heartwood color:** Grayish to light grayish-brown. Occasionally olive.

**Pore distribution:** Diffuse porous or semi-diffuse-porous. Usually an apparent size graduation from earlywood to latewood

**Pores:** Small to medium small; Solitary and in radial multiples of 2 to several

**Rays:** Very fine, not easily seen with hand lens

### Sycamore

*Platanus occidentalis*

**Average specific gravity:** 0.49

**Heartwood color:** Light to dark brown, usually with a reddish cast

**Pore distribution:** Diffuse-porous; growth rings distinct due to unusual lighter color of latewood (thinner band and clearer than beech)

**Pores:** Small, solitary and in irregular multiples and clusters, numerous and evenly distributed through-

out most of the growth ring; latewood zone evident by fewer, smaller pores

**Rays:** Easily visible without hand lens on all surfaces, appearing uniform in size and evenly spaced on transverse and tangential surfaces, producing conspicuous dark ray fleck on radial surfaces. Largest rays up to 14 seriate; uniseriate rays not common.

### **Sugar Maple**

*Acer saccharum*

**Average specific gravity:** 0.63

**Heartwood color:** Creamy white to light reddish-brown

**Pore distribution:** Diffuse-porous; growth rings distinct due to darker brown, narrow latewood line

**Pores:** Small, with largest approximately equal to maximum ray width in cross section; solitary or in radial multiples; very evenly distributed

**Rays:** Visible to eye on tangential surface as very fine, even-sized, evenly distributed lines; on radial surfaces, ray fleck usually conspicuous. Rays: Two distinct sizes: largest 7-8 seriate; uniseriate rays numerous.

### **Red Maple**

*Acer rubrum*

**Average specific gravity:** 0.54

**Heartwood color:** Creamy white to light reddish-brown, commonly with grayish cast or streaks.

**Pore distribution:** Diffuse-porous

**Pores:** Small, solitary and in radial multiples, very evenly distributed; largest as large or slightly larger than widest rays on cross section.

**Rays:** May be visible on tangential surface as very fine, even-sized and evenly spaced lines; on radial surface, ray fleck usually conspicuous. 1-5 seriate.

### **Yellow Birch**

*Betula alleghaniensis*

**Average specific gravity:** 0.62

**Heartwood color:** Light brown to dark brown, reddish-brown.

**Pore distribution:** Diffuse porous

**Pores:** Small to medium, solitary and in radial multiples of two to several pores

**Rays:** Rays smaller than pore diameters. Some pores may appear to be filled with a substance; 1-5 seriate.

### **Yellow Poplar**

*Liriodendron tulipifera*

**Average specific gravity:** 0.42

**Heartwood color:** Green, or yellow to tan with greenish cast

**Sapwood color:** creamy white (often wide)

**Pore distribution:** Diffuse-porous; growth rings delineated by distinct light cream or yellowish line of marginal parenchyma.

**Pores:** Small, solitary, but mostly in radial or irregular multiples and small clusters

**Rays:** Distinct on cross section with lens; produce conspicuous fine light ray fleck on radial surfaces. 1-5 (mostly 2-3) seriate

## **Softwood Identification**

### **Eastern White Pine**

*Pinus strobus*

**Average specific gravity:** 0.35

**Odor:** Pleasant, piney

**Heartwood:** Distinct, darkening with age

**Grain appearance:** Fairly even

**Earlywood / Latewood transition:** Gradual

**Resin Canals:** large, numerous, mostly solitary, evenly distributed

### **Southern Yellow Pine**

*Pinus spp.*

**Average specific gravity:** 0.51 to 0.61

**Odor:** "pitchy" pine odor

**Heartwood:** Distinct

**Grain appearance:** Uneven

**Earlywood / Latewood transition:** abrupt

**Resin Canals:** Large, numerous, mostly solitary, evenly distributed

### **Red Spruce**

*Picea rubens*

**Average specific gravity:** 0.40

**Odor:** None

**Heartwood:** Light in color; indistinct from sapwood

**Grain appearance:** Fairly even to moderately even

**Earlywood / Latewood transition:** Gradual

**Resin Canals:** Small, relatively few; solitary or several in tangential groups, variably distributed

**Hemlock**

*Tsuga Canadensis*

**Average specific gravity:** 0.40

**Odor:** None

**Heartwood:** Indistinct, light in color

**Grain appearance:** Fairly uneven

**Earlywood / Latewood transition:** Fairly abrupt  
to gradual

**Texture:** Medium to medium-coarse

**Balsam Fir**

*Abies balsamea*

**Average specific gravity:** 0.36

**Odor:** None

**Heartwood:** Indistinct, light in color

Grain appearance: moderately uneven to  
moderately even

**Earlywood / Latewood transition:** Very gradual

**Texture:** Medium

**Eastern Red Cedar**

*Juniperus virginiana*

**Average specific gravity:** 0.47

**Odor:** "cedar-chest" odor, very distinct

**Heartwood:** Distinct, deep purplish red, aging to  
reddish-brown

**Grain appearance:** Moderately uneven to fairly  
even; latewood narrow

**Earlywood / Latewood transition:** Gradual

**Texture:** Very fine

**Baldcypress**

*Taxodium distichum*

**Average specific gravity:** 0.46

**Odor:** Faint to moderately rancid

**Heartwood:** Usually distinct

**Grain appearance:** Uneven

**Earlywood / Latewood transition:** Abrupt; early-  
wood medium yellow-brown; latewood amber to  
dark brown

**Texture:** Coarse to very coarse

For more information or to inquire about  
wood identification short courses hosted by The  
University of Tennessee and the Tennessee  
Forest Products Center, please contact:

Dr. Brian H. Bond

Assistant Professor

The University of Tennessee

Tennessee Forest Products Center

2506 Jacob Drive

Knoxville, TN 37996-4563

Email : [bbond7@utk.edu](mailto:bbond7@utk.edu)


Website: <http://web.utk.edu/~tfpc/>

Phone: (865) 946-1121

Fax: (865) 974-4714

# SOFTWOOD KEY

(wood lacking pores)

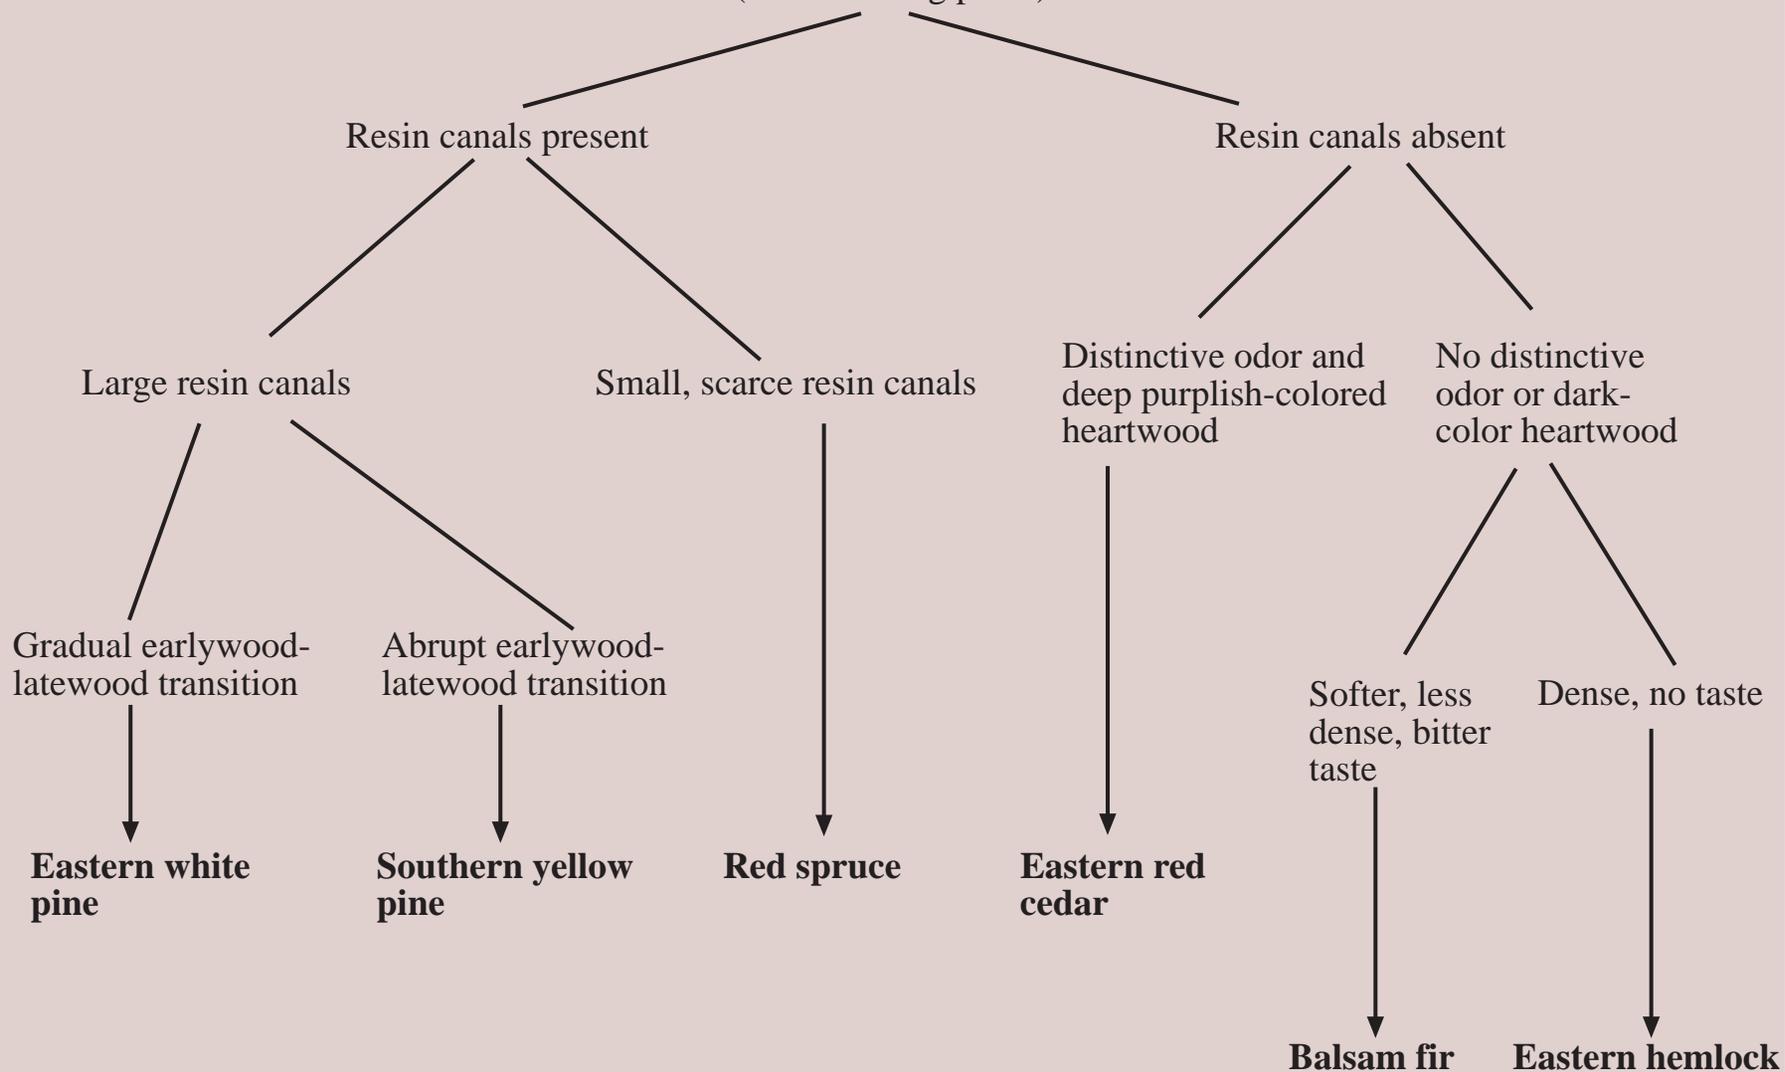

# HARDWOOD KEY

(wood with pores)

## Ring porous

## Semi-ring porous

## Diffuse porous

Pores in radial rows

Pores in wavy bands

Pores solitary or multiples

Tyloses absent or scarce

Tyloses present

Tyloses absent or scarce

Tyloses present

**Red oak**

**White oak**

**Ash**

**Elm**- earlywood/latewood transition very abrupt

**Hackberry**- earlywood/latewood transition more uneven

**Sweet (red) gum**- heartwood reddish brown, streaky; neither growth rings or rays distinct, extremely small pores

**Black gum (tupelo)**- heartwood darker grey with green or brown cast; otherwise indistinct

**Locust**- pores in nested groups

**Hickory**- very dense; also banded parenchyma for reticulate pattern on cross-section

**Walnut**- heartwood deep chocolate brown

**Beech**- larger rays more widely and irregularly spaced; latewood darker cast

**Sycamore**- rays more uniform in size and closely spaced; latewood has light cast

Both thick and narrow rays

Fine narrow rays

**Sugar (hard) maple**- cream color; very dense; very fine rays and slightly thicker rays

**Red (soft) maple**- less dense; rays all one size (very fine)

**Black cherry**- heartwood reddish, cinnamon brown; rays fine, distinct bright lines

**Yellow poplar**- heartwood moss green to yellowish green; growth rings distinct due to light colored marginal parenchyma

**Basswood**- soft, low density; marginal parenchyma at growth rings (spotty); faint musty odor

**Birch**- quite hard, dense; growth rings not distinct; rays barely visible to naked eye, pores solitary or in multiples

**Cottonwood**- soft, low density, medium-size pores; greyish light brown color, foul odor when moist

Visit the Agricultural Extension Service Web site at:  
<http://www.utextension.utk.edu/>

PB1692-1.5M-2/02      E12-4915-00-010-002

The Agricultural Extension Service offers its programs to all eligible persons regardless of race, color, national origin, sex, age, disability, religion or veteran status and is an Equal Opportunity Employer.

COOPERATIVE EXTENSION WORK IN AGRICULTURE AND HOME ECONOMICS

The University of Tennessee Institute of Agriculture, U.S. Department of Agriculture,  
and county governments cooperating in furtherance of Acts of May 8 and June 30, 1914.

Agricultural Extension Service Charles L. Norman, Dean